

Evaluation criteria for freezing and thawing of tunnel concrete lining according to theoretical and experimental analysis

Joon-Shik Moon^{1a}, Jai-Wook An^{*2}, Hong-Kyoon Kim^{2b}, Jong-Gun Lee^{2c} and Tim Lattner^{3d}

¹Department of Civil Engineering, Kyungpook National University, Daegu 41566, Republic of Korea

²Department of Ground Safety, KALIS, Gyeongsangnamdo 52852, Republic of Korea

³Office of Maintenance, DOT, State of Florida 32399-0450, USA

(Received December 17, 2021, Revised February 22, 2022, Accepted March 9, 2022)

Abstract. Abnormal climate events are occurring frequently around the world. In particular, cold waves and heavy snow lead to damage and deterioration of facilities, which can cause loss of life or property damage, such as shortening the lifespan of facilities. Therefore, it is very important to prepare an appropriate maintenance system and to establish a strategy to cope with abnormal weather conditions. In this study, laboratory freezing experiments were performed to analyze the freeze-thaw characteristics affecting the tunnel concrete lining, and heat flow analysis was carried out based on the test results. Based on these experimental and theoretical analysis results, quantitative freeze-thaw evaluation criteria for tunnel concrete linings were proposed.

Keywords: freeze-thaw evaluation criteria; freezing and thawing; fourier's law; heat flow analysis; thermal energy

1. Introduction

The main material used in tunnels is concrete, which is greatly affected by surrounding environmental conditions. Environmental conditions mainly refer to climatic conditions such as temperature, humidity, precipitation, wind, and sunshine duration. Also, the season change has a great influence on the deterioration of concrete material.

Many theories related to the freezing action of concrete have been proposed. Power (1945) used hydraulic pressure theory to explain the freezing mechanism in which the freezing of water inside the capillary pores and the resulting volume increase raises the internal tensile stress. According to the hydraulic theory, when the temperature of water drops below 0°C, the water in the concrete pores freezes, resulting in a volume increase of approximately 9%.

When the pores in the concrete are filled fully with water, the frozen water will be forced to escape because the pores cannot be expanded more. At this time, if the moving distance of water is too long or the internal pressure due to rapid freezing exceeds the tensile strength of the cement paste, the concrete may be destroyed. Power (1945) explained that freezing duration, not freezing rate, is important for concrete freezing, because the long freezing period promotes the crystal growth of the ice.

Bassuoni and Nehdi (2005) found that high-performance

concrete (HPC) with no air entrainment and low water-binding material ratio could not find any weak points from general freeze-durability tests. It is known that it is vulnerable to freeze-thaw resistance according to the mechanical degradation mechanism. Jeong (2013) explained that concrete damage caused by freeze-thaw does not occur because the average daily temperature is low. It is found that concrete tends to be damaged greatly by the relaxation of concrete tissue through the repeated freeze-thaw tests.

Jerzy *et al.* (2017) confirmed the number of repeated freezing-thawing days that can cause cracks in concrete by considering the correlation between the increase of concrete mass through repeated freeze-thaw cycles and cracks in concrete. Assel *et al.* (2021) conducted a comprehensive laboratory work to assess the effect of the cyclic freeze-thaw action on strength and durability of CSA cement-treated sand.

Jian *et al.* (2018) confirmed that the freeze-thaw repetition lowered the particle agglomeration and increased both the proportion of fine particles and the proportion of porous area through an experimental study. Liyun *et al.* (2020) compared the characteristics of the interface strength parameters during the freezing process and analyzed the differences between the interface shear characteristics and failure mechanisms during the frozen soil-structure interface freezing-thawing process.

Sammy *et al.* (1994) found that the absorbency and diffusivity of concrete were improved, while the resistance of concrete had the close relationship with the specific transmittance from the experimental test results for predicting the freeze-thaw resistance of concrete. Xudong *et al.* (2018) experimentally found that as the number of freeze-thaw cycles increased, the dynamic strength decreased and the peak strain increased.

*Corresponding author, Ph.D. General manager

E-mail: jwan@kalis.or.kr

^aAssociate Professor

^bPh.D. Executive manager

^cPh.D. Executive manager

^dP.E. Director

Table 1 Thermal conductivity and specific gravity of each material

matter	Thermal Conductivity (<i>W/m·K</i>)	Specific gravity	matter	Thermal Conductivity (<i>W/m·K</i>)	Specific gravity
silver	714	10.59	concrete	1.4	1.84
copper	657	8.94	Glass	1.21	-
gold	507	19.30	ice	2.18	0.92
aluminum	350	2.70	water	1.00	1.00
iron	86	7.80	tree	0.29	0.6~0.9
Mercury	14	11.34	air	0.04	0.0013

Table 2 Indoor freezing experimental plan

experimental factor		experimental level
Temperature measurement frequency		1 time / 5 minutes
Temperature sensor interval		Surface (internal) temperature measurement Internal temperature measurement: 75 mm, 150 mm, 225 mm Back (outer) temperature measurement
Concrete Lining Temperature	initial temperature	Above 5°C
	target temperature	Below -2.2°C
Setting outside temperature		-13°C ~ -18 °C
concrete lining specimen	target thickness	30 0 mm
	target air volume	6.0% or higher
	goal slump	180 mm or more
	target intensity	More than 27 Mpa

Hailong and Nanguo (2019) reviewed the effects of mechanical loads and harmful environmental factors on concrete by examining the coupling and synergistic mechanisms between the degradation driving forces such as freeze-thaw and alkali-silica reactions.

Francesco *et al.* (2014) conducted a study to identify and quantify specific effects on deterioration and aging of concrete in order to provide useful information for the evaluation of structures.

2. Theoretical background

Freezing and thawing are one of the most problematic factors among the causes of deterioration in tunnel linings. In particular, in the case of regions where the winter temperature is relatively low, as the public service life of the tunnel increases, there is a possibility that the damage through repeated freezing and thawing may increase rapidly. Therefore, it is necessary to identify areas where damage is expected from freezing and thawing and prepare appropriate countermeasures.

2.1 Heat conduction in concrete

Conduction or heat conduction is the transfer of heat through direct contact between objects. Conduction is a method in which heat (energy) flows by the temperature difference between two objects in contact without direct movement of materials. Conduction may occur from one end to the other within an object, or may occur through a tertiary object.

On a microscopic scale, conduction is the transfer of heat (energy) through the interaction of rapidly vibrating or moving atoms or molecules with neighboring atoms or molecules. Heat is transferred as neighboring atoms vibrate with respect to another atom, or electrons move from one atom to another. Conduction occurs in all states of matter (solid, liquid, gas, etc.), but in solids it is the most important heat transfer method. The law that explains the phenomenon of heat conduction is called the 'law of heat conduction' or 'Fourier law'.

The amount of heat transferred between two objects per unit time is proportional to the temperature difference between the two objects and the contact cross-sectional area and inversely proportional to the distance. Let the unit time be Δt , the amount of heat transferred is ΔQ , the temperature difference between the two objects is ΔT , the contact cross-sectional area is A , and the distance is Δx .

$$\frac{\Delta Q}{\Delta t} = -kA \frac{\Delta T}{\Delta x} \quad (1)$$

In the equation expressing Fourier's law, k , which is a proportionality constant appears, because each object has a different property of conducting heat. This comparison of the degree of heat transfer between materials at the same temperature difference and distance is called thermal conductivity. The larger the value, the better the heat conduction. For reference, the unit of thermal conductivity is $W/m·K$ obtained by dividing the unit of heat (W , *Watt*) by the product of the unit of distance (m , *meter*) and the unit of temperature (K , *Kelvin*). Materials with high thermal conductivity are called good conductors of heat, and

substances with low thermal conductivity are called insulators (or poor conductors) of heat. Table 1 shows the ductile conductivity and specific gravity for each material, and it was confirmed that the thermal conductivity of concrete is generally 1.4.

3. Indoor freezing experiment

3.1 Experimental plan

In this freezing test, concrete specimens were manufactured, exposed to sub-zero temperatures, and the internal and external temperatures of concrete that change with time were measured. Based on the heat transfer energy according to the outside temperature at this time, the freezing time of the concrete linings is predicted.

Table 2 describes the contents of the experimental level for each experimental factor for conducting the indoor freezing test.

3.2 Manufacture of concrete specimen for freezing test

The concrete specimen for use in the indoor freezing test was manufactured to satisfy the actual concrete lining design criteria. In general, it is a standard to set the minimum thickness of the concrete lining to be about 300 mm. In the case of standard strength, in principle, concrete with a strength of 21-24 *Mpa* at 28 days of age is generally used as the standard strength, but in some cases, it is more high-strength concrete can be used. The thickness of the concrete specimen produced for the indoor experiment is 300 mm, the 28-day-old strength is 36.4 *Mpa*, and the slump is 190 mm. The concrete mixing ratio is as shown in Tables 3 and 4.

3.3 Experimental method

This indoor freezing experiment was carried out to measure the time it takes for the temperature of the lining and the back surface, which was maintained in the freezing state of the concrete lining in winter due to the temperature of the outside air, to drop to a constant temperature below zero and the temperature change at this time. The temperature change of the concrete specimen was measured through a temperature sensor installed inside and outside the concrete, and the measurement cycle was set at 5-minute intervals.

Table 3 Concrete mixing ratio

W/C(%)	unit weight (kg/m ³)					slump(mm)	air content(%)
	C	W	S	G	ad		
48	354	170	819	941	2.66	190	6.5

Table 4 Concrete specimen compressive strength

3 days	7 days	28 days
20.1 Mpa	32.7 Mpa	36.4 Mpa

The test conditions were conducted when the temperature of the tunnel outside air was about -13 to -18°C, and the temperature was below zero, and a total of 5 sensors for measuring the temperature change were installed on the surface of the concrete specimen and at intervals of 75 mm from the surface. lower surface, 75 mm, 150 mm, 225 mm, upper surface) were installed.

4. Results and analysis of indoor freezing experiment

4.1 Analysis of freezing time of concrete specimen according to indoor freezing test

A total of 2 sets of indoor experiments were conducted. The concrete specimen was maintained at about 5.5°C and 6.6°C. As shown in Table 5, the FHWA evaluates the freezing standards of concrete based on when the concrete changes to a temperature of -2.2°C or less. According to the FHWA standard, the time required to change the temperature of the concrete specimen to a temperature of -2.2°C or lower was measured. In addition, the amount of heat flow (*W*) required to freeze the specimen was analyzed based on the experimental results. Through heat flow analysis, the energy required to change the temperature of the concrete specimen can be calculated at the outside temperature, and if the conditions are the same, the freezing time according to the change of the outside temperature can be predicted according to the law of conservation of energy.

Through the freezing test, it was confirmed that it took about 30.5 hours and 32.6 hours as shown in Table 6 for the total temperature of specimen No. 1 at 5.5°C and specimen No.2 at 6.5°C to change to -2.2°C. The time taken to change from the surface of the specimen to -2.2°C or less by depth was reviewed as taking an average of 10.30 hours in the 75 mm section, 18.00 hours in the 150 mm section, 26.96 hours in the 225 mm section, and 31.54 hours on the back of the specimen. Figs. 1 and 2 show the temperature change patterns of specimens No.1 and No.2 according to the results of the freezing test, respectively.

4.2 Analysis of temperature change by depth of concrete specimen

In the indoor freezing test, the change in the internal temperature was measured at a depth of 75 mm from the surface of the specimen, and the time required to lower the internal temperature in each section to about -2.2 °C was measured.

Table 5 Freeze-Thaw evaluation criteria of FHWA

Exposure Condition	Classification		
	a(N/A)	b(Grade 1)	c(Grade 2)
Freeze/Thaw Durability Exposure ($x=F/T$ cycles per year*)	$x < 3$	$3 \leq x < 50$	$50 \leq x$

**F/T* stands for "freeze/thaw". A freeze/thaw cycle is defined as an event where saturated concrete is subjected to an ambient temperature which drops below -2.2°C (28°F) followed by a rise in temperature above freezing

Table 6 Time for the concrete specimen(No.1, 2) to change to -2.2°C

Division	surface of the specimen	75 mm	150 mm	225 mm	back surface of the specimen
Specimen No. 1 (Back temperature 5.5°C)	Immediately	10.42	17.42	25.75	30.50
Test Subject No.2 (Back temperature 6.5°C)	Immediately	10.17	18.58	28.17	32.58
Average	-	10.30	18.00	26.96	31.54

Table 7 Average freezing time of concrete specimens

Classification	Specimen temperature								
	5°C	4°C	3°C	2°C	1°C	0°C	-1°C	-2°C	
75 mm	0°C	5.79	5.04	4.08	3.04	1.71	-	-	-
	-1°C	8.08	7.33	6.38	5.33	4.00	2.29	-	-
	-2°C	10.25	9.50	8.54	7.50	6.17	4.46	2.17	-
	-2.2°C	10.83	10.08	9.13	8.08	6.75	5.04	2.75	0.58
150 mm	0°C	10.13	8.42	6.67	4.54	2.33	-	-	-
	-1°C	12.79	11.08	9.33	7.21	5.00	2.67	-	-
	-2°C	15.79	14.08	12.33	10.21	8.00	5.67	3.00	-
	-2.2°C	16.79	15.08	13.33	11.21	9.00	6.67	4.00	1.00
225 mm	0°C	11.88	9.63	7.38	5.00	2.79	-	-	-
	-1°C	16.83	14.58	12.33	9.96	7.75	4.96	-	-
	-2°C	22.58	20.33	18.08	15.71	13.50	10.71	5.75	-
	-2.2°C	23.38	21.13	18.88	16.50	14.29	11.50	6.54	0.79
back surface of specimen	0°C	17.17	14.75	12.46	9.79	5.92	-	-	-
	-1°C	22.17	19.75	17.46	14.79	10.92	5.00	-	-
	-2°C	26.38	23.96	21.67	19.00	15.13	9.21	4.21	-
	-2.2°C	27.33	24.92	22.63	19.96	16.08	10.17	5.17	0.96

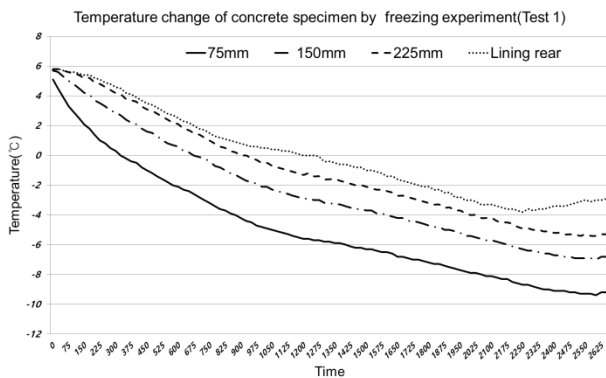


Fig. 1 Temperature change analysis result of concrete specimen No.1

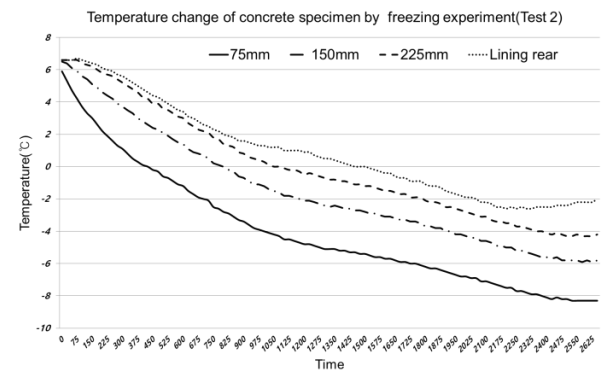


Fig. 2 Temperature change analysis result of concrete specimen No.2

The main cause of defects in concrete due to freeze-thaw is the expansion pressure generated by freezing of the water contained in the concrete. When water freezes, about 9% of volume expansion occurs, and when the amount of expansion of water is greater than the voids in the concrete, if the expansion pressure is greater than the tensile strength of the concrete, defects such as cracks and scaling occur.

In general, water has a minimum volume at 4°C, and has a maximum volume after freezing at 0°C. In other words, it can be interpreted that from when the temperature of the concrete is below about 0°C, the influence of the expansion pressure inside the concrete is relatively large.

Table 7 is a table that summarizes the freezing time according to the temperature of each section of the concrete specimen. The temperature of each section was measured at every 1°C from 5°C to -2°C, and the freezing time from the surface to the 75 mm point was measured. It took an average of 10.25 hours at the 75 mm point for the concrete to change from the temperature of 5°C to -2°C at the temperature of the concrete specimen, 15.79 hours at the 150 mm point, and 22.58 hours at the 225 mm point on average.

When the outdoor temperature of the tunnel is about 16°C, it is judged that the time it takes for the surface to freeze is about 10 hours. In the case of winter, when nights are longer, it is judged that the surface of the tunnel lining will freeze frequently after the sun goes down.

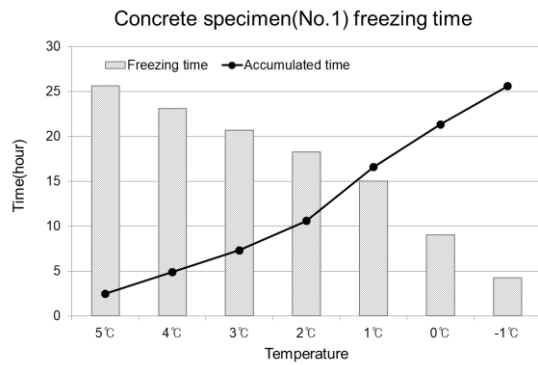


Fig. 4 Analysis of freezing time by temperature of concrete specimen No. 1

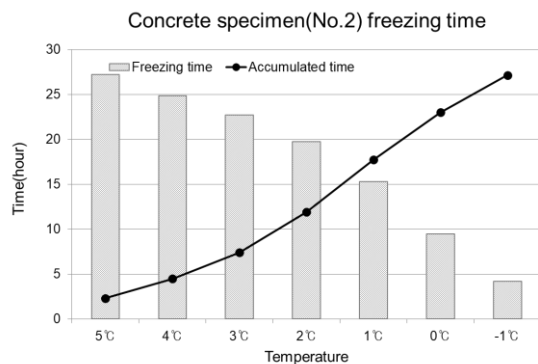


Fig. 4 Analysis of freezing time by temperature of concrete specimen No. 2

4.3 Freezing time analysis according to the back surface of the concrete specimen

By analyzing the temperature change and time measured through the indoor freezing experiment, it was confirmed how the moisture in the concrete affected the freezing time of the concrete specimen.

It took about 11.25 hours for the back temperature of the concrete specimen to decrease by about 4°C from 5°C to 1°C, and it was confirmed that it takes an average of 2.81 hours for a change of 1°C. And it took about 10.92 hours to decrease about 2°C from 1°C to -1°C, confirming that it takes an average of 5.46 hours for a change of 1°C.

This is considered to be related to the time at which the moisture inside the concrete freezes. Through the experiment, it was confirmed that the time it takes for the concrete specimen to decrease by 1°C at the freezing point is about twice as long as the time it takes to decrease by 1°C at the freezing point.

Figs. 3 and 4 are graphs showing the freezing time of the concrete specimen, and it can be seen that the cumulative freezing time increases as the concrete specimen approaches the freezing point of 0°C.

4.4 Heat flow analysis according to heat conduction theory

The heat transfer acting to freeze the concrete specimen refers to the flow of energy generated by the temperature

Table 8 Analysis result of average energy required to change the temperature of a concrete specimen by 1°C

classification	surface (T2)	Back surface (T1)	time (second)	Qcond(W) (J/s)	Energy (J)
Average energy required for 1°C temperature change	-13.27°C	5°C	-	-	-
	-14.14°C	4°C	8,700	7.25	63,072
	-14.90°C	3°C	8,250	7.20	59,372
	-16.01°C	2°C	9,600	7.10	68,141
	-16.98°C	1°C	13,950	7.14	99,784
	-17.61°C	0°C	21,300	7.13	151,916
	-18.14°C	-1°C	18,000	6.98	125,507
	-18.45°C	-2°C	15,150	6.78	102,710
	-	-2.2°C	3,450	6.83	23,565
	Average	-16.19	-	-	7.05
sum	-	-	-	-	694,067

difference between the surface and the back surface of the specimen cooled due to the external temperature maintained below zero. The concrete specimen is frozen due to the convection phenomenon caused by the sub-zero outside temperature, and the lowered concrete surface is frozen through the inside of the concrete to the back side.

In the case of heat conduction occurring inside concrete, the amount of heat energy transferred can be known through Fourier's law. The equation used at this time is the heat flow (W) equation and is the same as Eq. (2).

$$Q_{cond} = -kA \frac{\Delta T}{\Delta x} \quad (2)$$

Here, k is the thermal conductivity of concrete and the unit is $W/m \cdot K$. In this paper, the thermal conductivity of commonly used concrete of 1.4 was applied. ΔT is the difference ($T1-T2$) between the temperature ($T1$) of the surface of the concrete specimen and the temperature of the back of the concrete ($T2$), ΔX is the thickness of the concrete specimen, and A is the area exposed to the outside air in the specimen. Q_{cond} is the amount of heat generated in concrete, and the unit is W (watt), meaning that $1J$ (joule) of energy is generated for 1 second.

The area of the concrete specimen used in the freezing test is 300 mm×300 mm, and the thickness is 300 mm. The amount of heat flow was calculated based on the results of measuring the temperature change and time of the concrete specimen through the freezing test, and the energy required to lower the temperature of the concrete backside by 1°C was calculated. Table 8 shows the average values of heat flow and energy calculated through the results of two experiments.

According to the experimental results, the average heat flow required to freeze all concrete specimens to -2.2°C was about 7.05W, and the average heat energy generated at this time was calculated to be 694,067J. Based on the thermal energy calculated in this way, we want to predict the freezing time of concrete when the temperature of the outside air changes.

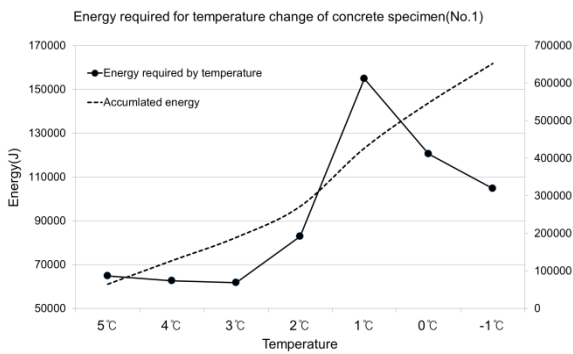


Fig. 5 Thermal energy consumption by temperature of concrete specimen No. 1

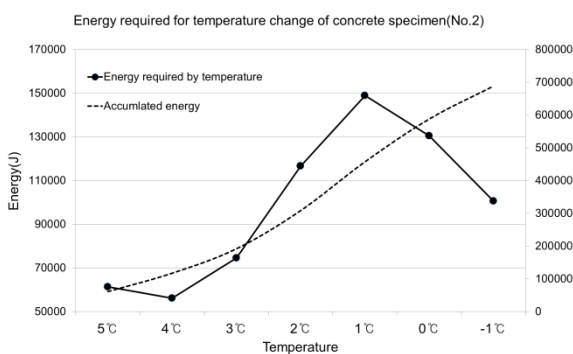


Fig. 6 Thermal energy consumption by temperature of concrete specimen No. 6

4.5 Analysis of energy required for freezing concrete lining

The actual tunnel lining temperature will vary depending on the temperature of the outside air and the temperature of the back ground. Therefore, the temperature of the outside air, the exposure time and the temperature of the back surface will be important factors in the condition that all the concrete linings are frozen.

The outdoor temperature in the indoor freezing test varies from about -13°C to -18°C , and the average is about -16.2°C . The temperature of the back side of the concrete can be measured from 5.5°C and 6.5°C . Based on the results of measuring the freezing time of all concrete specimens under these temperature conditions, Fourier's Law was used to calculate the energy required to lower the concrete surface temperature by 1°C .

The thermal energy required to lower the back temperature of concrete by about 4°C from 5°C to 1°C was $290,369\text{J}$, and the average thermal energy required to lower about 1°C was calculated as $72,592\text{J}$. In addition, the thermal energy required to decrease by about 2°C from 1°C to -1°C is $277,423\text{J}$, and the average thermal energy required to lower the temperature by 1°C was calculated as $138,712\text{J}$.

These results are considered to be related to the time at which the moisture inside the concrete freezes. Figs. 5 and 6 show the thermal energy required for the temperature

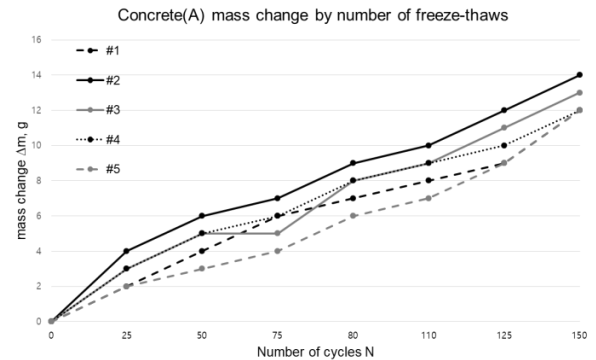


Fig. 7 Change in mass of concrete specimen A according to the number of freezing-thaws (Jerzy 2017)

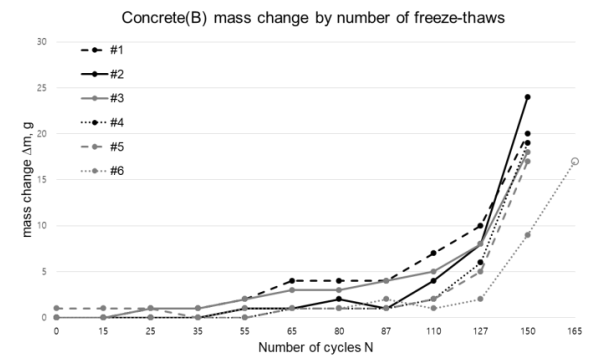


Fig. 8 Change in mass of concrete specimen B according to the number of freezing-thaws (Jerzy 2017)

change calculated as result of the freezing tests of specimens No. 1 and 2 respectively, and it can be seen that the required thermal energy increases as the concrete specimen approaches the freezing point of 0°C .

5. Concrete lining freeze-thaw evaluation criteria

5.1 Selection of the required duration for freezing of concrete lining

In order to select the temperature conditions required for freezing of the concrete lining, the freezing time of concrete for each outdoor temperature was predicted using the thermal energy calculated based on the results of the freezing experiment.

The temperature of the lining of the tunnel will be distributed in various ways, such as the temperature of the outside air and the condition of the back ground. Therefore, the temperature condition of the back surface of the concrete was selected from 5°C to 1°C , and the freezing temperature of the concrete was selected from 0°C to -2.2°C .

The Korea Meteorological Administration observes the temperature every hour, and the average daily temperature is the average of the values observed every 3 hours.

When evaluating the temperature conditions required for freezing, it is judged that it is appropriate to use the daily average temperature of each region.

Table 9 Concrete lining freezing condition analysis result by outside temperature

outside temperature	concrete temperature	freezing temperature	duration (day)	outside temperature	concrete temperature	freezing temperature	duration (day)
-19°C	5°C	-2.2°C	0.99	-11°C	3°C	-1°C	1.10
-18°C	5°C	-2.2°C	1.05	-11°C	1°C	-2°C	1.04
-18°C	4°C	-2°C	1.03	-10°C	2°C	-1°C	1.05
-18°C	4°C	-2°C	0.98	-9°C	5°C	-2°C	2.02
-17°C	5°C	-2°C	1.07	-9°C	4°C	-2.2°C	1.98
-17°C	4°C	-2.2°C	1.03	-8°C	3°C	-2.2°C	2.09
-17°C	4°C	-2°C	0.98	-8°C	3°C	-2°C	1.98
-16°C	4°C	-2.2°C	1.09	-8°C	1°C	-1°C	1.02
-16°C	4°C	-2°C	1.05	-7°C	2°C	-2°C	2.08
-16°C	3°C	-2.2°C	1.01	-6°C	5°C	-2°C	3.08
-15°C	5°C	-1°C	0.99	-6°C	4°C	-2.2°C	3.08
-15°C	3°C	-2.2°C	1.08	-6°C	1°C	-2°C	2.10
-15°C	3°C	-2°C	1.03	-5°C	5°C	-2.2°C	4.00
-14°C	5°C	-1°C	1.06	-5°C	2°C	-2°C	3.10
-14°C	3°C	-2°C	1.10	-4°C	4°C	-2.2°C	5.07
-14°C	2°C	-2.2°C	1.04	-4°C	3°C	-1°C	3.06
-14°C	2°C	-2°C	0.98	-4°C	1°C	-2.2°C	3.98
-13°C	4°C	-1°C	1.03	-3°C	4°C	-2.2°C	8.10
-13°C	2°C	-2°C	1.06	-3°C	3°C	-2°C	7.02
-12°C	3°C	-1°C	1.01	-3°C	2°C	-2°C	5.96
-12°C	1°C	-2.2°C	1.01	-	-	-	-

Table 9 is a table summarizing the temperature and duration required to freeze each concrete. In order to calculate the evaluation criteria using the average daily temperature, the duration was selected based on 24 hours (1 day).

In the case of Gangwon, the coldest region in Korea, the average annual temperature in winter is about -1.73°C , and it is assumed that the temperature of the backside of the concrete lining of the tunnel is used to maintain the backside temperature in the winter at about $1\sim 2^{\circ}\text{C}$. The temperature condition is conservatively judged to be about 2°C . In addition, as a criterion for selecting the freezing temperature, the freezing point of water, 0°C , and the concrete damage mechanism due to the freezing of moisture in the concrete were taken into consideration and a safety level of about -2°C or higher was selected.

Therefore, among the temperature conditions and durations summarized in Table 9, the most representative freezing conditions were analyzed when lasting for about 24 hours at -14°C , lasting for about 48 hours at -7°C , and lasting for about 72 hours at -5°C .

In the case of concrete specimen A, it shows a periodic increase in mass from the start of freezing. This indicates the formation of cracks in the rapid deterioration process and the absorption of moisture accordingly. At this time, micro-cracks were observed on the surface of the specimen. Table 10 summarizes the number of freeze-thaw repetitions required to reach a limited mass increase.

The evaluation of the decrease in durability due to freeze-thaw is to measure the change in mass, and through this, it is possible to determine the number of freeze-thaw

Table 10 Number of freeze-thaws related to concrete deterioration (Jerzy 2017)

Properties	Concrete A	Concrete B
	Number for $\Delta m = 10 \text{ g}$	Number for $\Delta m = 12 \text{ g}$
Sample #1	133	132
Sample #2	108	133
Sample #3	116	138
Sample #4	124	140
Sample #5	133	143
Sample #6	-	158
Average	122.8	140.7

repetitions that can cause fatal damage corresponding to a decrease in strength of about 20%.

In general, the minimum lifespan of concrete structures is stipulated as about 30 years, so if the number of freeze-thaw cycles exceeds 4.1 to 4.7 times per year, structural damage may occur. These results are intended to be used in the evaluation of the evaluation criteria for the number of freeze-thaw repeated days presented in this paper.

5.3 Selection of freeze-thaw evaluation criteria considering the climate

Based on the freezing time of the concrete lining according to the ambient temperature confirmed through the indoor freezing test, the temperature conditions of the outside air of the tunnel required to freeze the concrete lining are -14°C , -7°C and -5°C , and the duration of each is 24 hours, 48 hours and 72 hours.

Table 11 Tunnel freeze-Thaw environmental evaluation standard

Classification	Evaluation grade				
	a	b	c	d	e
Number of freeze-thaw repetitions(F)* (F= Number of freeze-thaw repetitions per year)	F<1.5	1.5≤F<3	3≤F<4.5	4.5≤F<6	6≤F

*The number of freeze-thaw repetitions (F) can be applied differently for each region, and typical conditions are as follows

The melting conditions of the concrete lining were selected when the temperature outside the tunnel was about 0°C or higher for 24 hours, and each freeze-thaw condition is as follows.

1. In the case of lasting more than 1 days at -14°C and then 1 day at 0°C or higher

2. In the case of lasting more than 2 days at -7°C and then 1 day at 0°C or higher

3. In the case of lasting more than 3 days at -5°C and then 1 day at 0°C or higher

The number of repetitions that tunnel lining can cause structural defects through freezing and thawing is about 123 to 141 times. Assuming that the minimum lifespan of the tunnel is 30 years, if it is repeated about 4.1 to 4.7 times per year on average, structural defects due to freeze-thaw may occur after 30 years. Tunnels in public use in Korea are maintained through periodic inspection and diagnosis, so it would be reasonable to select the maximum number of freeze-thaw repetitions that tunnel linings can overcome as a value of 141 or less for safety. Therefore, it was selected as the number of freeze-thaw repetitions that can cause structural defects when repeated about 140 times.

In addition, it will be necessary to consider the period of use after the tunnel facility is completed. That is, by selecting the evaluation criteria including the concept of time, it will be possible to suggest whether to secure the durability against the occurrence of freeze-thaw damage at the time of evaluation. Therefore, it will be necessary to evaluate the freeze-thaw risk of the tunnel through evaluation of how close it is to the maximum of 140 by calculating the number of repetitions of freezing and thawing from the time when the structure is completed to the time of evaluation.

1. In the case of lasting more than 1 days at -14°C and then 1 day at 0°C or higher

2. In the case of lasting more than 2 days at -7°C and then 1 day at 0°C or higher

3. In the case of lasting more than 3 days at -5°C and then 1 day at 0°C or higher

As the degree of damage from freeze-thaw is determined according to the climatic conditions of each region, it is possible to classify the freeze-thaw risk areas by region in Korea. The maximum number of freeze-thaw repetitions that cause deterioration in the tunnel structure is 140. Accordingly, the case where the concrete structure is repeated 140 times or more during the minimum lifespan of 30 years was calculated as d grade. The evaluation grade was selected based on about 4.5 times a year considering

the safety side. The selected freeze-thaw environmental evaluation criteria are shown in Table 11.

6. Conclusions

In this study, quantitative environmental evaluation criteria for freezing and thawing that can be used in the design and maintenance of tunnels are proposed. The main conclusions of this study are summarized as follows.

1. Moisture inside the concrete increases by about 9% when it freezes. Accordingly, when the pores are filled with water, the expansion pressure is generated due to the volume increase during freezing, and the concrete is damaged. This deterioration of concrete is further aggravated by freezing duration and repetition of freeze-thaw.

2. Freezing tests were performed to find out the time it takes for the tunnel concrete lining to reach the freezing conditions. It took about 27.33 hours to freeze the concrete specimen from 5°C to -2.2°C.

3. It was found that it took 11.25 hours for the temperature of the back surface of the concrete specimen to decrease by about 4°C from 5°C to 1°C. It took 10.92 hours for the first 2°C decrease, which is about 5.46 hours/°C.

4. From the result of heat flow analysis using Fourier's law, the average heat flow (W) required to change the concrete specimen from 5°C to -2.2°C was analyzed as 7.05, and the total required heat energy was 694,067J.

5. The thermal energy required to decrease the temperature of the back side of the concrete specimen by about 4°C from 5°C to 1°C is 290,369J, indicating that an average of 72,952J of thermal energy is required to decrease by 1°C. In addition, the thermal energy required for a decrease of about 2°C from 1°C to -1°C was 277,423J, indicating that an average of 138,712J of thermal energy was required for a 1°C decrease.

6. Based on the analysis results of the freezing time of the concrete lining, the freezing conditions of the concrete lining were reached after 1 day at -14°C, 2 days at -7°C, or 3 days at -5°C.

7. Based on the research result that the deterioration of concrete proceeds rapidly when freeze-thaw is repeated about 140 times, the critical number of freeze-thaw repetitions was proposed. Since the service life of the tunnel is about 30 years in Korea, if the freezing and thawing of concrete lining is repeated about 4.5 times a year, the tunnel structure may be damaged.

8. In areas with the freeze-thaw environmental evaluation grade C or lower, it is necessary to design the tunnel to ensure durability against freeze-thaw. In addition, for tunnels of grade C or lower, the maintenance strategy for freeze-thaw damage should be established.

Acknowledgments

This research was supported by the Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education (NRF-2020R111A3071653).

References

- Assel, J., Nazerke, S., Kim, J., Ku, T.S. and Moon, S.W. (2021), "Performance of cement-stabilized sand subjected to freeze-thaw cycles", *Geomech. Eng.*, **25**(1), 41-48. <https://doi.org/10.12989/gae.2021.25.1.041>
- Bassuoni, M.T. and Nehdi, M.L. (2005), "The case for air-entrainment in highperformance concrete", *Proceedings of the Institution of Civil Engineers, Structures & Buildings*, **158**(5), 311-319. <https://doi.org/10.1680/stbu.2005.158.5.311>
- Federal Highway Administration (1998), "High-performance Concrete Defined for Highway Structures", High-Performance Concrete Committee Special Report No. 4, U.S.A
- Francesco, P., Giuseppina, U., Andrea, F. and Mauro, M. (2014), "Assessment of concrete degradation in existing structures: a practical procedure", *Struct. Eng. Mech.*, **52**(4), 701-721. <https://doi.org/10.12989/sem.2014.52.4.701>
- Hailong, Y. and Nanguo, J. (2019), "Degradation mechanisms of concrete subjected to combined environmental and mechanical actions: a review and perspective", *Comput. Concrete*, **23**(2), 107-119. <https://doi.org/10.12989/cac.2019.23.2.107>
- Jeong, H.M. (2013), "Degree of damage risk by freeze and thaw of concrete structures in Korea", Journal of the Korea Concrete Institute 2013
- Jerzy, W. and Agnieszka, M. (2017), "Evaluation of concrete resistance to freeze-thaw based on probabilistic analysis of damage", *Procedia Eng.*, **193**, 35-41. <https://doi.org/10.1016/j.proeng.2017.06.183>
- Jian, X., Zhangquan, W., Jianwei, R. and Jun, Y. (2018), "Mechanism of shear strength deterioration of loess during freeze-thaw cycling", *Geomech. Eng.*, **14**(4), 307-314. <https://doi.org/10.12989/gae.2018.14.4.307>
- Jin, H.W. and Hwang, Y.C. (2017), "A study on current extent of damage of road tunnel lining in cold regions", *KGES*, **18**(1), 49-58. <https://doi.org/10.14481/jkges.2017.18.1.49>
- Liyun, T., Yang, D., Land, L., Liujun, Y. and Guoyu, L. (2020), "Effect mechanism of unfrozen water on the frozen soil-structure interface during the freezing-thawing process", *Geomech. Eng.*, **22**(3), 245-254. <https://doi.org/10.12989/gae.2020.22.3.245>
- Park, K.H., An, J.W., Park, S.H. and Yoon, T.G. (2017), "A study on the development of maintenance system for tunnel with freezing-thawing damage", *GEDMAR*, 121-135. <https://doi.org/10.6140/9789864371419.201710.0011>
- Powers, T C. (1945), "A working hypothesis for further studies of frost resistance." Journal of the American Concrete Institute
- Sammy, Y.N.C., Ravindra, K.D., Peter, C.H. and Chang, D.Y. (1994), "Near surface characteristics of concrete: prediction of freeze/thaw resistance", *Struct. Eng. Mech.*, **2**(4), 403-412. <https://doi.org/10.12989/sem.1994.2.4.403>
- Xudong, C., Chen, C., Zhiheng, L., Jun, L. and Xiangqian, F. (2018), "Compressive behavior of concrete under high strain after freeze-thaw cycle", *Comput. Concrete*, **21**(2), 209-217. <https://doi.org/10.12989/cac.2018.21.2.209>
- Zhang, X., Yu, W., Wang, C. and Liu, Z. (2006), "Three-dimensional nonlinear analysis of coupled problem of heat transfer in the surrounding rock and heat convection between the air and the surrounding rock in the Fenghuo mountain tunnel", *Cold Reg. Sci. Technol.*, **44**(1), 38-51. <https://doi.org/10.1016/j.coldregions.2005.07.002>